

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106 1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client :	Birrus Matting Systems				
	12 Overseas Dve				
	Noble Park North VIC 3174				

16-003127 Test Number : **Issue Date** 05/07/2016 : **Print Date** 5/07/2016 :

Sample Description	Clients Ref : "Duramat" Matting
	Colour : Silver/Black
	Nominal Composition : Aluminium/PVC Nitrile
	Nominal Thickness : 10mm

AS/ISO 9239.1-2003


Reaction to Fire Tests for Floorings. Determination of the Burning Behaviour using a **Radiant Heat Source**

Date of Sample Arrival Date Tested	14/06/2016 04/07/2016				
CHF Value	1	2	3	Mean	
Length	10.8	10.8	10.8	10.8	kW/m²
Width	≥11.0	-	-	-	kW/m²
Smoke Value	1	2	3	Mean	
Length	416	413	416	415	%.min
Width	277	-	-	-	%.min
Glowing				Yes	

The test results relate to the behaviour of the test specimens of a product under the particular conditions of the test, they are not intended to be sole criterion for assessing the potential fire hazard of the product in use.

Sample was conditioned in accordance with BSEN 13238:2001 at a temperature of 23±2°C and relative humidity of 50±5% for a minimum of 48 hours prior to testing.

Each specimen was clamped to a substrate of 6mm thick fibre reinforced cement board prior to testing.

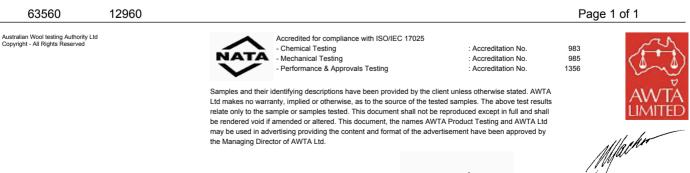

APPROVED SIGNATORY

SADY

C

63560